

# Evaluation Low Cost Adsorbent of Walnut Bark Granule for Methylene Blue Dye Removal from Aqueous Environments

Ali Almasi<sup>a</sup>, Farhad Amirian<sup>b</sup>, Mitra Mohammadi<sup>a</sup>, Ahmad Reza Yari<sup>c</sup>, Abdollah Dargahi<sup>\*d</sup>, Ghobad Ahmadidoust<sup>e</sup>

<sup>a</sup>Department of Environmental Health Engineering, School of Public Health, Kermanshah University of Medical Sciences, Kermanshah, Iran.

<sup>b</sup>Department of pathology, School of Medicine, Kermanshah University of Medical Sciences, Kermanshah, Iran.

<sup>c</sup>Research Center for Environmental Pollutants, Qom University of Medical Sciences, Qom, Iran.

<sup>d</sup>Department of Environmental Health Engineering, School of Public Health, Ardabil University of Medical Sciences, Ardabil, Iran.

<sup>e</sup>Department of Environmental Health Engineering, School of Public Health, Hamadan University of Medical Sciences, Hamadan, Iran.

\*Correspondence should be addressed to Dr. Abdollah Dargahi, Email: [a.dargahi29@yahoo.com](mailto:a.dargahi29@yahoo.com)

## A-R-T-I-C-L-E-I-N-F-O

### Article Notes:

Received: Jan17, 2018

Received in revised form:  
Mar 24, 2018

Accepted: Apr 21, 2018

Available Online: May 1,  
2018

### Keywords:

Adsorbent,  
Walnut Bark Granule,  
Methylene Blue,  
Aqueous environments,  
Iran.

## A-B-S-T-R-A-C-T

**Background & Aims of the Study:** Methylene blue (MB) is a risk for human and environment. Adsorption process is one of the removal mechanisms of MB. The purpose of this research was the evaluation of low cost adsorbent of walnut bark granule for MB dye removal from aqueous environments.

**Materials & Methods:** In this experimental research, the effect of various operating parameters such as dose of dye (100-500 mg/L), contact time (10-50 min), adsorbent dosage (1-5 g/L) and pH (3-8) was investigated. Color concentration was measured by spectrophotometer (Shimadzu Model UV-120-02) at 663 nm wavelength and pH was analyzed through pH meter (Digimed model DM-20, Digicron AnaliticaLtda, Sao Paulo, Brazil).

**Results:** The findings of this research were showed that the walnut bark granule was able to remove up to 41% of MB dye (100 mg/L) from solutions at initial pH 7. Removal efficiency was increased by adsorbent dosage and contact time. MB concentration has a reverse effect on removal. Also, the equilibrium data were also fitted to the Freundlich equilibrium isotherm model ( $R^2=0.95$ ).

**Conclusions:** Present study showed that use of walnut bark granule, as an adsorbent, could be utilized in methylene blue removal. Therefore, considering the production wastes of this compound, utilization the essence of this substance as inexpensive adsorbent with inexpensive and available raw material is clear.


**Please cite this article as:** Almasi A, Amirian F, Mohammadi M, Yari AR, Dargahi A, Ahmadidoust G. Evaluation Low Cost Adsorbent of Walnut Bark Granule for Methylene Blue Dye Removal from Aqueous Environments. Arch Hyg Sci 2018;7(2):112-117.

## Background

Due to increasing industrial activities, the increase of contaminated water sources are considered as environmental problems such as chemical oxygen demand (COD) by the water body, and an increase in toxicity(1). Methylene

blue (MB) that belongs to cationic dye classification of thiazine, used in textile, paper, plastics, food industries and medicine (Fig.1) (2). Sewage released by these industries pollutes and colorize the fresh water of streams, rivers and underground water (3). MB has not biodegradability and cause environmental

problems to the water sources. Thus, color may still remain in the effluent (2,4).

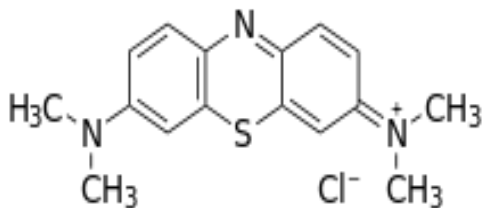

**Figure 1) Molecular structure of methylene blue.**

Colored effluent caused to damages the aesthetic nature of the water surface and lowering photosynthesis (4). Dyes may cause skin irritation, dysfunction of brain, reproductive effects on kidney; also, have mutagenic and carcinogenic effects, too (5,6). As most of these dyes are hazardous and toxic to living aquatic organisms and human, removal of them has become vital (5). Various physical (6,7), chemical (8-10) and biological (11,12) methods were used for MB reduction from water and wastewater. At actual scale, most of them are not applicable because of the high cost and complexity instrument (13). Adsorption process has been employed for color and toxic compounds removal from wastewater, successfully (14). During the adsorption, as simple and prepare method, the pollutants are adsorbed on the surface of the adsorbent (15). Adsorption is inexpensive and has not sensitivity to the toxins and simpler implementation ability (16). The carbon, derived from low cost wastes, is important as appropriate materials for the removal of organic and inorganic contaminants from wastewater. Waste plant biomass can be utilized to produce activated carbon (17). Various low cost adsorbents for MB removal has developed such as clay (18), yeast (19), Carica papaya seeds (20), carbon Nanotubes (21), chitosan/oil palm Ash (22), leaf palm (23) raw pummelo peel (24), miswak leaves (25) and so on. Annually, high amount of walnut bark as waste evacuated. Others study shown walnut bark has functional group such OH and H that adsorb organic compounds (26).

#### **Aims of the study:**

The objective of the present study was the investigation of walnut bark granule (WBG) potential as an available adsorbent for the removal of MB from aqueous environments.

#### **Materials & Methods**

In the experimental study, initially walnut bark samples were milled and subsequently by 20-70 mesh were screened and 1-3 mm particles were separated and collected. In order to removing impurities, milled samples were rinsed times by  $\text{NaHCO}_3$ , 0.1  $\text{NHCl}$  and distilled water; then, dried at 105 degrees celsius for 2 hr. Methylene blue removal by walnut bark granule was studied in discontinuous system at different contact times. Methylene blue dyes with analytical grade were purchased from Merck Co. In order to determine the pH absorbent, 5 g/L sample prepared in distilled water and preserved in laboratory conditions for 24 hours. Then, pH values of solution at 3-8 range read by pH-meter (Digimed model DM-20, Digicron AnaliticaLtda, Sao Paulo, Brazil) at six levels. In order to determine the efficiency of processed walnut bark granule in methylene blue removal, initially 5 flasks containing 100 ml of 0.1 mg/L methylene blue solution added to each flask. Then, 1-5 g/L absorbent added to flasks No. 1 to 5 respectively and stirred for 10 min at 300 rpm. After 10 min, flasks containing separately filtered by Watman filter paper and filtered solution transferred into tubes. After transferring solutions on filter paper, flasks were stirred for 10 min again. After a second stirring, flask containing was filtered. Similar steps were repeated for third, fourth and fifth 10 min (30, 40 and 50 min) and flasks residual solutions were filtered. Finally, absorption of 25 tubes measured by spectrophotometer Shimadzu Model UV-120-02 at 663 nm wavelength. In order to processing walnut bark, five dye concentrations (100, 200, 300, 400 and 500 mg/L) were utilized. Each experiment had three replications and mean of measurements were reported as final result. In the present research, effect of various parameters such as

proper contact time, adsorbent dose and various concentrations of dye were studied. After determination of proper contact time and adsorbent dose, properties related to absorption isotherm on processed powder of walnut bark were determined. Absorption isotherms were studied using Freundlich and Longmuir equations.

## Results

The effect of pH on methylene blue removal was presented in figure 2. As can be seen in figure 2, methylene blue removal affected by pH; so, by increasing pH from 3 to 6, methylene blue removal increased on adsorbent surface and at maximum pH values removal decreased. PH value of 7 was selected as optimal for the afterward experiments.

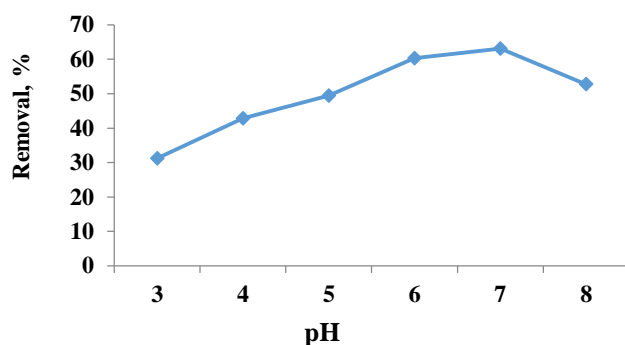


Figure 2) Effect of pH on methylene blue removal (contact time: 50 min, adsorbent dosage: 5 gr/L, methylene blue concentration: 100 mg/L)

The effect of time on methylene blue removal was presented in Figure 3. Results showed that by increasing contact time from 10 min to 50 min, methylene removal increased, so that highest removal obtained as 31.2% at 50 min time and 100 mg/L methylene blue and the lowest amount by 5% obtained in 10 min and 500 mg/L methylene blue (Fig. 3).

In order to determine the adsorbent dose on methylene blue removal, various amounts of adsorbent were exposed to 100-500 mg/L methylene blue (Fig. 4).

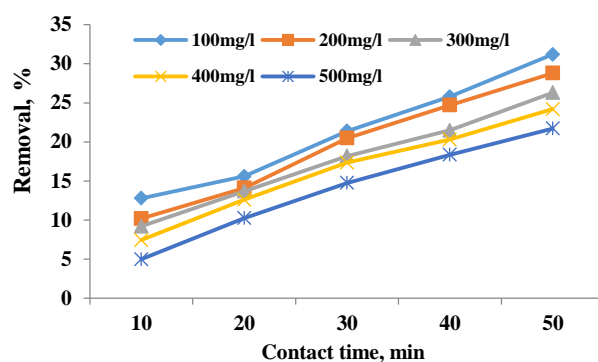


Figure 3) Effect of contact time on methylene blue removal (pH: 7, adsorbent dosage: 5 gr/L)

Finding showed that increasing adsorbent dose from 1 to 5 gr resulted to increase in methylene blue removal; so, the highest removal by 41% obtained in adsorbent dose, 5 gr, methylene blue concentration, 100 mg/L, the lowest amount obtained by 1 gr adsorbent and 500 mg/L methylene blue as 5.88%. Adsorption isotherms are mathematical equation for explaining the equilibrium state of adsorbate between solid and liquid phase. Experimental data for adsorption equilibrium were studied by Freundlich and Longmuir adsorption isotherms. Results showed that methylene blue adsorption on studied adsorbent follows Freundlich isotherm ( $R^2 = 95\%$ ).

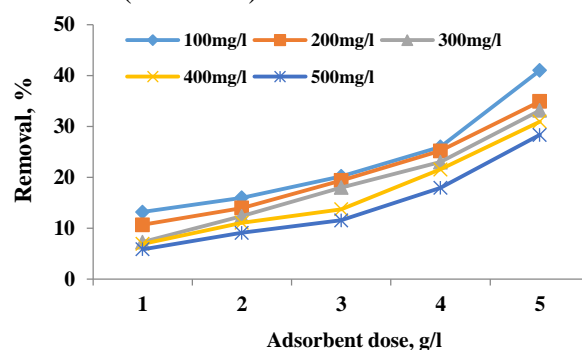


Figure 4) Effect of adsorbent dosage on methylene blue removal (pH: 7, contact time: 50 min)

## Discussion

Various factors such as pH, contact time, initial dose of pollutant and adsorbent dose affect sorption process. Therefore, in the present study the impacts of above mentioned factors on methylene blue removal via walnut bark

granules were evaluated. pH is an important factor which affects sorption process through affecting pollutant structure and absorbent surface charge. Sorption process affected by initial pH of the solution; so, as pH increased to 7, removal efficiency increased but in higher pH values, we observed decreasing in removal efficiency. The reason for decreasing methylene blue removal at higher pH values than 7 could be attributed to increasing OH ion which results in decreasing electrostatic bonding power between methylene blue molecules and absorbent surface (27). One of the other effective parameters on sorption is absorbent dose. In the present study, by increasing absorbent dose from 1 to 5 g/L in standard solution, methylene blue removal efficiency increased. Increasing the removal efficiency resulted from increasing absorbent dose could be explained such that by increasing absorbent dose; there is more surface area which could be resulted to increasing removal efficiency (28). Initial dye concentration provided a considerable motive power for overcoming to resistance resulted from mass transfer among solid and liquid phases. Results of studying the methylene blue concentration showed that methylene blue removal efficiency decreased by increasing initial concentration which is due to this fact that absorbents have limited sorption sites which will be more saturated by increasing the initial concentration and removal efficiency would be decreased (29). Contact time is one of the main effective parameters in practical applications in sorption process. As can be observed in the present study, surface sorption capacity and methylene blue removal percent via absorbent rapidly increased at initial stages; then, increased slower according to increasing time up to reaching to equilibrium within 50 min. The highest methylene blue removal efficiency obtained at 50 min contact time by 41 percent. Generally, pollutants removal rate initially was rapid and gradually decreased by the time and eventually reached to equilibrium.

This event resulted from this fact that at initial stages there are so many sorption sites which are empty for absorption, while by increasing the process time, the void sites in the absorbent surface will saturated which could be due to inhibitory powers among absorbed molecules on solid and liquid absorbent surface (30). In this research, 5 g/L absorbent dose, contact time of 50 min and 100 mg/L methylene blue concentration were selected as optimum conditions. Absorption isotherms show absorbent molecules fraction in equilibrium state among solid and liquid phases (31). In Long-Muir model, a layer of dissolved molecules absorbed on absorbent surface and at all surfaces, the similar absorption energy and reversible absorption bonds were assumed and in Freundlich model, areas on absorbent surface are not uniform and have different sorption power (32). Results of isotherm researches showed that correlation coefficient of Freundlich isotherm equation was very high ( $R^2=0.95$ ). Therefore, it can be stated that methylene blue removal was not a one-layer reaction and follows Freundlich equation.

## Conclusion

Present study showed that use of walnut bark granule as an absorbent could be utilized in methylene blue removal. In colored wastewaters containing methylene blue, studied absorbent could be utilized in small water treatment facilities as supplemental stage. Walnut bark provides well sorption active sites through an appropriate porosity.

## Footnotes

### Acknowledgement:

Authors are gratefully acknowledged experts of chemistry laboratories in the Environmental Health Engineering Department, Kermanshah University of Medical Sciences.

### Conflict of Interest:

The Authors have no conflict of interest.

## References

- Godini H, Dargahi A, Mohammadi M, Shams Khorramabadi G, Azizi A, Tabande L, et al. Efficiency of Powdery Activated carbon in Ammonia-Nitrogen Removal from Aqueous Environments (Response Surface Methodology). Arch Hyg Sci 2017;6(2):111-120.
- Dahri MK, Kooh MRR, Lim LB. Application of Casuarina equisetifolia needle for the removal of methylene blue and malachite green dyes from aqueous solution. Alex Eng J 2015;54(4):1253-63.
- Nadi H, Alizadeh M, Ahmadabadi M, Yari AR, Hashemi S. Removal of Reactive Dyes (Green, Orange, and Yellow) from Aqueous Solutions by Peanut Shell Powder as a Natural Adsorbent. Arch Hyg Sci 2012;1(2):41-47.
- Seidmohammadi A, Asgari G, Leili M, Dargahi A, Mobarakian A. Effectiveness of Quercus Branti Activated Carbon in Removal of Methylene Blue from Aqueous Solutions. Arch Hyg Sci 2015;4(4):217-225.
- Weng CH, Pan YF. Adsorption of a cationic dye (methylene blue) onto spent activated clay. J Hazardous Mater 2007;144(1):355-62.
- Asadi F, Dargahi A, Almasi A, Moghohfe E. Red Reactive 2 Dye Removal from Aqueous Solutions by Pumice as a Low-Cost and Available Adsorbent. Arch Hyg Sci 2016;5(3):145-152.
- Feddal I, Ramdani A, Taleb S, Gaigneaux EM, Batis N, Ghaffour N. Adsorption capacity of methylene blue, an organic pollutant, by montmorillonite clay. Desalination Water Treat 2014;52(13-15):2654-61.
- Jin YZ, Zhang YF, Li W. Micro-electrolysis technology for industrial wastewater treatment. J Environ Sci (China) 2003;15(3):334-8.
- Crini G. Studies on adsorption of dyes on beta-cyclodextrin polymer. Bioresour Technol 2003;90(2):193-8.
- Mishra A, Bajpai M. The flocculation performance of Tamarindus mucilage in relation to removal of vat and direct dyes. Bioresour Technol 2006;97(8):1055-9.
- Owamah HI, Chukwujindu IS, Asiagwu AK. Biosorptive capacity of yam peels waste for the removal of dye from aqueous solutions. Civ Environ Res 2013;3(1):3648.
- Mohammed MA, Shitu A, Ibrahim A. Removal of methylene blue using low cost adsorbent: A review. Res J Chem Sci 2014;4(1):91-102.
- Almasi A, Pirsahab M, Haghghi SA, Sharafi K, Moradi M, Jabari Y. Modeling and Statistical Analysis of Malachite Green Dye Removal from Aqueous Solutions by Activated Carbon Powder Prepared from Pine Bark (Modified by Sulfuric Acid) Application of Response Surface Methodology. Int Res J Appl Basic Sci 2016;10(1):5-12.
- Jafari Mansoorian H, Jonidi Jafari A, Yari AR, Mahvi AH, Alizadeh M, Sahebhan H. Application of Acaciatorilis Shuck as of Low-cost Adsorbent to Removal of Azo Dyes Reactive Red 198 and Blue 19 from Aqueous Solution. Arch Hyg Sci. 2014;3(1):1-11.
- Kavitha D, Namasivayam C. Capacity of activated carbon in the removal of acid brilliant blue: Determination of equilibrium and kinetic model parameters. Chem Eng J 2008;139(3):453-61.
- Song J, Zou W, Bian Y, Su F, Han R. Adsorption characteristics of methylene blue by peanut husk in batch and column modes. Desalination 2011;265(1-3):119-25.
- Santhy K, Selvapathy P. Removal of reactive dyes from wastewater by adsorption on coir pith activated carbon. Bioresour Technol 2006;97(11):1329-36.
- Shirsath SR, Patil AP, Patil R, Naik JB, Gogate PR, Sonawane SH. Removal of Brilliant Green from wastewater using conventional and ultrasonically prepared poly (acrylic acid) hydrogel loaded with kaolin clay: a comparative study. Ultrason Sonochem 2013;20(3):914-23.
- Ghaedi M, Hajati S, Barazesh B, Karimi F, Ghezlbash Gh. Saccharomyces cerevisiae for the biosorption of basic dyes from binary component systems and the high order derivative spectrophotometric method for simultaneous analysis of Brilliant green and Methylene blue. Ind Eng Chem 2013;19(1):227-33.
- Unuabonah EI, Adie GU, Onah LO, Adeyemi OG. Multistage optimization of the adsorption of methylene blue dye onto defatted Carica papaya seeds. Chem Eng J 2009;155(3):567-79.
- Gupta VK, Kumar R, Nayak A, Saleh TA, Barakat M. Adsorptive removal of dyes from aqueous solution onto carbon nanotubes: A review. Adv Colloid Interface Sci 2013;193-194:24-34.
- Hasan M, Ahmad A, Hameed B. Adsorption of reactive dye onto cross-linked chitosan/oil palm ash composite beads. Chem Eng J 2008;136(2-3):164-72.
- Alavi SN, Shamshiri S, Zahra Pariz AD, Mohamadi M, Fathi S, Amirian T. Evaluating the palm leaves efficiency as a natural adsorbent for removing cadmium from aqueous solutions: Isotherm adsorption study. Int J Pharm Technol 2016;8(2):13919-29.
- Hu C, Li J, Zhou Y, Li M, Xue F, Li H. Enhanced removal of methylene blue from aqueous solution by pummelo peel pretreated with sodium hydroxide. J Health Sci 2009;55(4):619-24.
- Elmorsi TM. Equilibrium isotherms and kinetic studies of removal of methylene blue dye by adsorption onto miswak leaves as a natural adsorbent. J Environ Prot 2011;2(6):817.

26. Liu J, Meng M, Li C, Huang X, Di D. Simultaneous determination of three diarylheptanoids and an  $\alpha$ -tetralone derivative in the green walnut husks (*Juglans regia* L.) by high-performance liquid chromatography with photodiode array detector. *J Chromatogr A* 2008;1190(1-2):80-5.
27. Rafatullah M, Sulaiman O, Hashim R, Ahmad A. Adsorption of methylene blue on low-cost adsorbents: a review. *J Hazard Mater* 2010;177(1-3):70-80.
28. Asgari G, Dargahi A, Mobarakian SA. Equilibrium and Synthetic Equations for Index Removal of Methylene Blue Using Activated Carbon from Oak Fruit Bark. *J Mazandaran Univ Med Sci* 2015;24(121):172-87. (Full Text in Persian)
29. Aksu Z, Karabayır G. Comparison of biosorption properties of different kinds of fungi for the removal of Gryfalan Black RL metal-complex dye. *Bioresour Technol* 2008;99(16):7730-41.
30. Cengiz S, Cavas L. Removal of methylene blue by invasive marine seaweed: *Caulerpa racemosa* var. *cylindracea*. *Bioresour Technol* 2008;99(7):2357-63.
31. Ponnusami V, Madhuram R, Krithika V, Srivastava S. Effects of process variables on kinetics of methylene blue sorption onto untreated guava (*Psidium guajava*) leaf powder: statistical analysis. *Chem Eng J* 2008;140(1):609-13.
32. Demirbas E, Kobya M, Sulak MT. Adsorption kinetics of a basic dye from aqueous solutions onto apricot stone activated carbon. *Bioresour Technol* 2008;99(13):5368-73.